

KYNAR® PVDF and KYNAR FLEX® PVDF

***Superior
Permeation
Barriers***



THE OVERALL SUCCESS OF A CONTAINMENT MATERIAL IS DEPENDENT ON A COMBINATION OF IMPORTANT PROPERTIES:

- The material must maintain its physical properties over time, e.g., resist stiffening or cracking
- The material must resist swelling and weight gain
- The material must not dissolve or soften
- The material must not abrade away or particulate from chemical flow
- The material must not allow permeation through the containment barrier

PERMEATION THROUGH KYNAR PVDF POLYMERS

Permeation is influenced by the phase of the matter being contained. Gas phases tend to be more permeable than liquid phases. For Kynar® PVDF as a containment barrier, permeation of gases or liquids is influenced by:

- **The thickness of the polymer barrier layer:** Permeation is generally given in rates per thousandth of an inch (mils) or millimeters (mm) of barrier thickness. Regardless of the permeation resistance of the polymer, thicker barriers tend to provide lower permeation rates.
- **Surface effects of the polymer:** Materials with a fluorinated surface, like Kynar PVDF, increase the contact angle of many fluids and thus have lower permeation rates through the polymer.
- **Crystallinity of the polymer:** For Kynar and Kynar Flex PVDF polymers, the greater the crystallinity, the lower the permeation through the polymer barrier.
- **Concentration:** Chemicals in solution can sometimes be pulled through the barrier by the solvent. A smaller solvent molecule will sometimes swell the polymer and allow a larger molecule to pass through. High concentrations of small molecules have greater permeation rates than low concentrations of large molecules.
- **Temperature:** Permeation rates increase with temperature. For any barrier, the permeation rate at the highest anticipated temperature should determine the design of the barrier system.
- **Pressure:** Higher pressures within the containment vessel will increase permeation rates through the polymer barrier.
- **Polarity:** Along with molecular size, molecular polarity plays a key role in permeation through polymer barriers. Kynar PVDF is somewhat polar (~ 1.0–1.7) and will thus be quite resistant to benzene, Cl₂, Br₂, O₂, N₂, H₂, especially with compared with non-polar fluoropolymers (PTFE, PFA, FEP) and non-polar polyolefins (PE, PB, PP). High crystallinity gives Kynar PVDF reasonably good resistance to even very polar chemicals like methanol and sulfuric acid.

PUBLISHED DATA

Two definitive data tables have been published showing the permeation resistance of various polymers to specific gases and liquid:

GAS PERMEABILITY OF FLUOROPOLYMERS*

Data based on 100 µm film thickness at 23°C. Method: ASTM D1434 for gases.

Water vapor according to DIN 53122. PVDF film is made by Westlake Plastics from Kynar® PVDF.

	PTFE	PFA	FEP	ETFE	CTFE	ECTFE	PVDF	PVF
Water Vapor g/m ² .d.bar	5	8	1	2	1	2	2	7
Air cm ³ /m ² .d.bar	2000	1150	600	175	x	40	7	50
Oxygen cm ³ /m ² .d.bar	1500	x	2900	350	60	100	20	12
Nitrogen cm ³ /m ² .d.bar	500	x	1200	120	10	40	30	1
Helium cm ³ /m ² .d.bar	3500	17000	18000	3700	x	3500	600	300
Carbon Dioxide cm ³ /m ² .d.bar	15000	7000	4700	1300	150	400	100	60



* Data published on 1980 Kunststoffe paper entitled Fluorocarbon Films—Present Situation and Future Outlook.
x = Not tested

VARIOUS LIQUID PERMEATION RATES IN CORROSIVE CHEMICALS

(Source Southwest Research Institute) (test 30mil tubes static 28 days/672 hours)

AMBIENT PERMEATION RATES (g-cm/hr/m)						
	Chloroform	Methanol	Toluene	HCL	Hydrochloride	Bromine
Kynar Flex® 2800	<1X10 ⁻⁵	<1X10 ⁻⁵	<1X10 ⁻⁵	<1X10 ⁻⁵	<1X10 ⁻⁵	<1X10 ⁻⁵
Kynar Flex® 2850	<1X10 ⁻⁵	<1X10 ⁻⁵	0.00004	<1X10 ⁻⁵	<1X10 ⁻⁵	<1X10 ⁻⁵
Kynar® 740	< 1 x 10 ⁻⁵	<1X10 ⁻⁵	<1X10 ⁻⁵	<1X10 ⁻⁵	<1X10 ⁻⁵	0.00026

66°C PERMEATION RATES (g-cm/hr/m)					
	Chloroform	Methanol	Toluene	HCL	Hydrochloride
Kynar Flex® 2800	0.177716	0.16340	0.05972	0.01621	0.00347
Kynar Flex® 2850	0.09386	0.11966	0.03488	0.01226	0.00258
Kynar® 740	0.02142	0.00063	0.00966	0.02930	0.00170

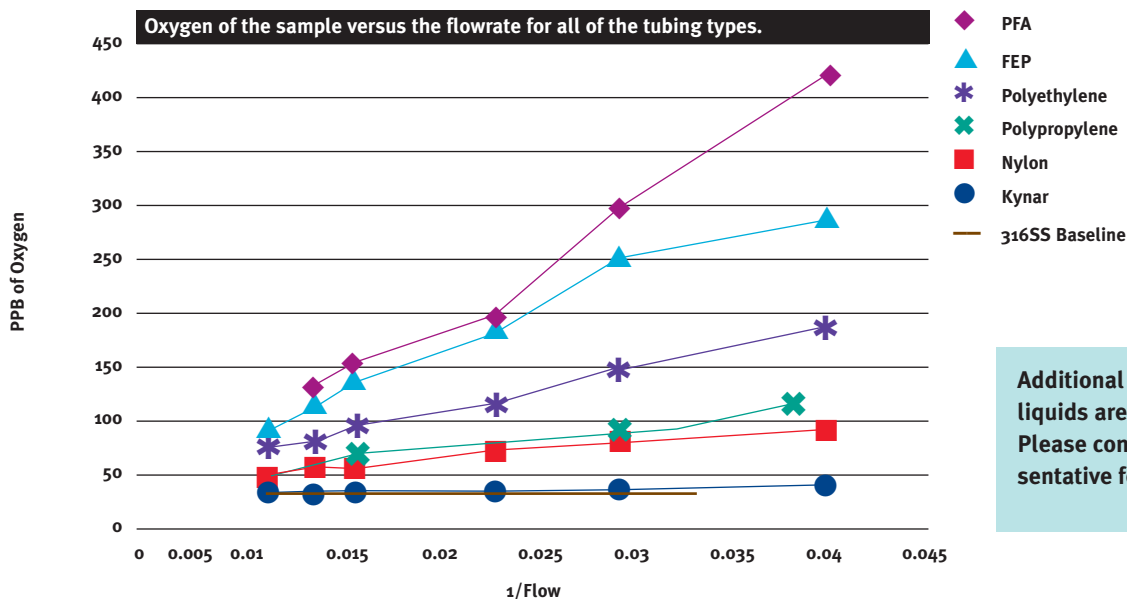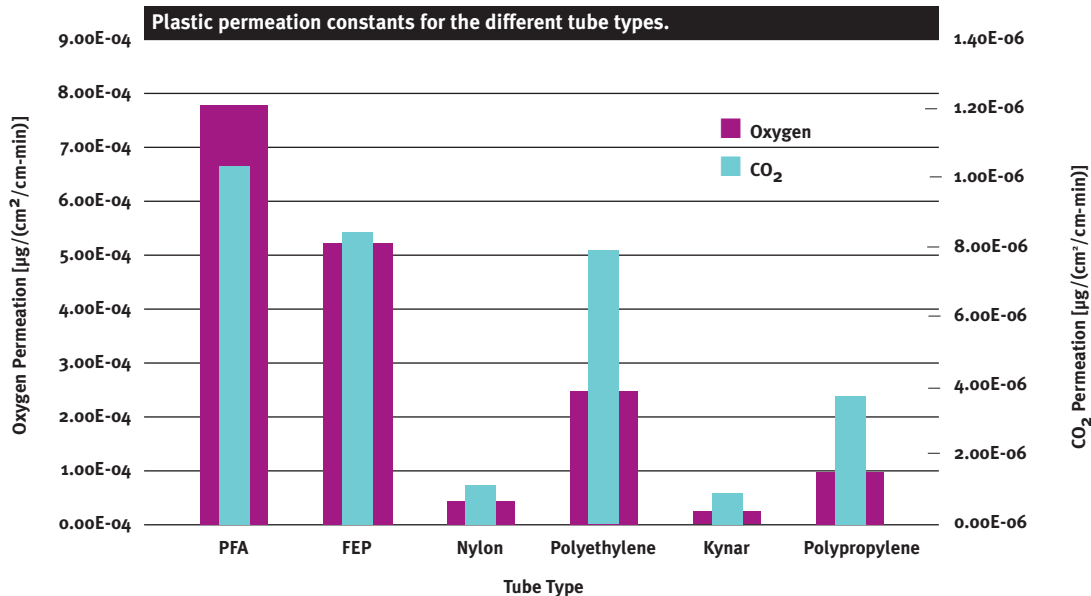

Additional data for other gases and liquids are available on request. Please consult an Arkema Inc representative for further details.

PERMEATION CONSTANTS				PERMEATION RATES Micrograms/min. through plastic sheet, 1 cm thick, with an area of cm ²			
Plastic Type	Oxygen (O ₂)*	Carbon Dioxide (CO ₂)*	Water**	Plastic Type	Oxygen (O ₂)*	Carbon Dioxide (CO ₂)*	Water**
PFA	1.56E-8	1.42E-8	1.08E-7	PFA	7.81E-4	1.05E-6	2.58E-5
FEP	1.08E-8	1.11E-8	7.08E-8	FEP	5.13E-4	8.23E-7	1.69E-5
Polyethylene	5.07E-9	1.06E-9	8.92E-8	Polyethylene	2.4E-4	7.83E-7	2.13E-5
Polypropylene	1.96E-9	4.9E-9	2.45E-8	Polypropylene	9.28E-5	3.64E-7	5.85E-6
Nylon	8.25E-10	1.41E-9	2.16E-6	Nylon	3.9E-5	1.05E-7	5.17E-4
PVDF	1.84E-10	1.8E-10	2.24E-10	PVDF	8.68E-6	8.39E-8	5.35E-8

*from experimental data **estimated from literature by ratio of water-to oxygen rates

Source: UltraPure Water Journal, December 2000, Vol. 17, No. 10

Note: 8.68E-6 means 8.68 *10 to the -6th power

The statements, technical information and recommendations contained herein are believed to be accurate as of the date hereof. Since the conditions and methods of use of the product and of the information referred to herein are beyond our control, Arkema expressly disclaims any and all liability as to any results obtained or arising from any use of the product or reliance on such information; NO WARRANTY OF FITNESS FOR ANY PARTICULAR PURPOSE, WARRANTY OF MERCHANTABILITY OR ANY OTHER WARRANTY, EXPRESS OR IMPLIED, IS MADE CONCERNING THE GOODS DESCRIBED OR THE INFORMATION PROVIDED HEREIN. The information provided herein relates only to the specific product designated and may not be applicable when such product is used in combination with other materials or in any process. The user should thoroughly test any application before commercialization. Nothing contained herein should be construed as an inducement to infringe any patent and the user is advised to take appropriate steps to be sure that any proposed use of the product will not result in patent infringement.

See MSDS for Health & Safety Considerations

© 2006 Arkema Inc. All rights reserved.



Arkema Inc.
2000 Market Street
Philadelphia, PA 19103
Tel.: 215-419-7000
www.Arkema-Inc.com